

# Observation of Trions in Monolayer WS<sub>2</sub> via Time-Resolved Terahertz Spectroscopy

Jon K. Gustafson and L. Michael Hayden


Department of Physics, UMBC, 1000 Hilltop Circle, Baltimore, MD 21250



## Introduction

**Carrier Dynamics:** How charges behave in a material under the influence of an electric field


**Monolayer:** A single layer of molecules

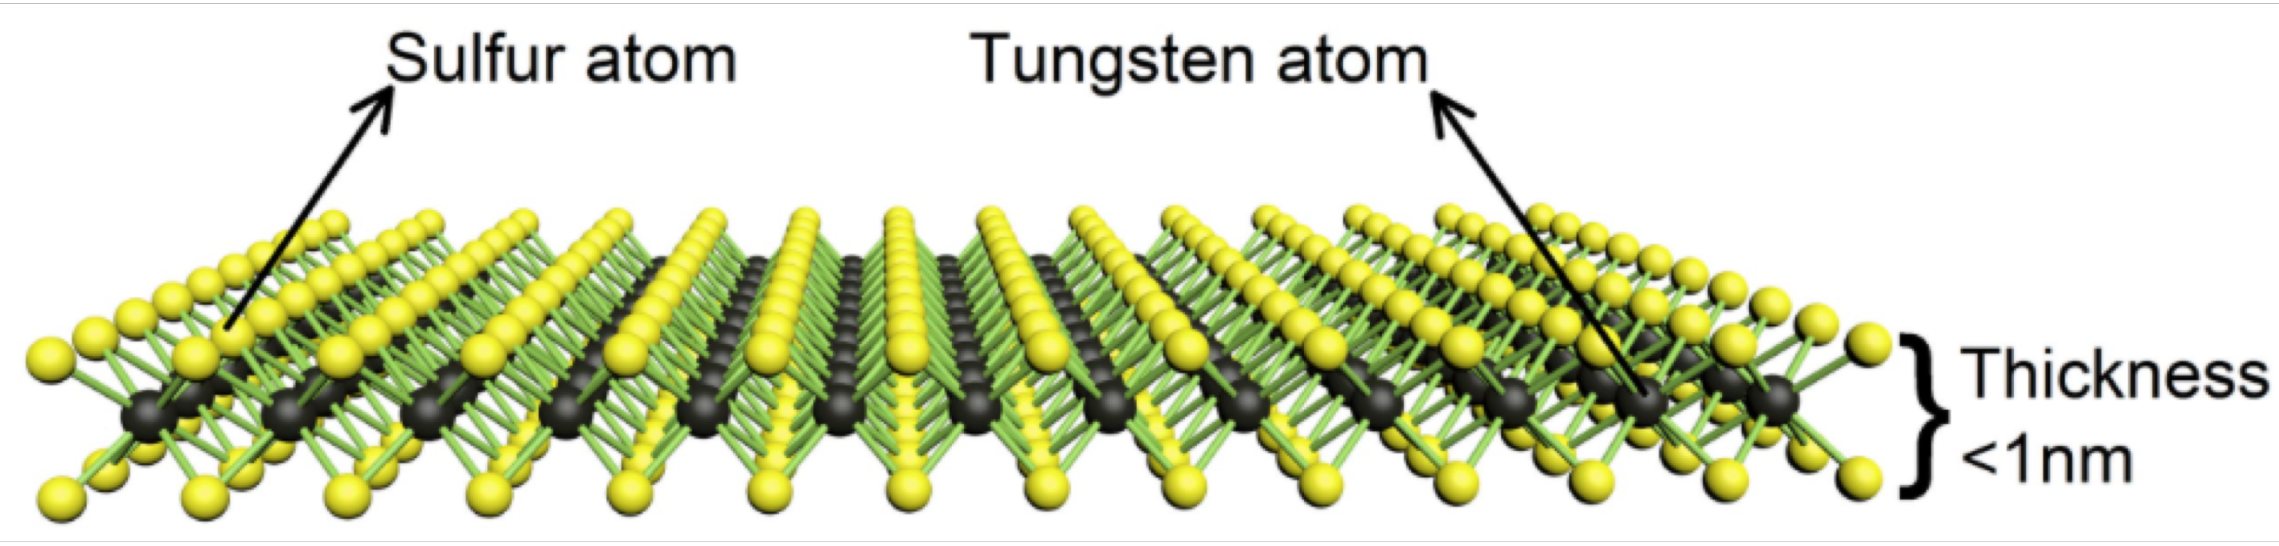

**Device Applications:** High-speed optoelectronics  
Field-effect transistors  
Photovoltaics


## Properties of WS<sub>2</sub>

- Reduced dielectric screening results in the existence of tightly bound excitons at room temperature
- Strong Coulombic interactions support charged excitons (trions)

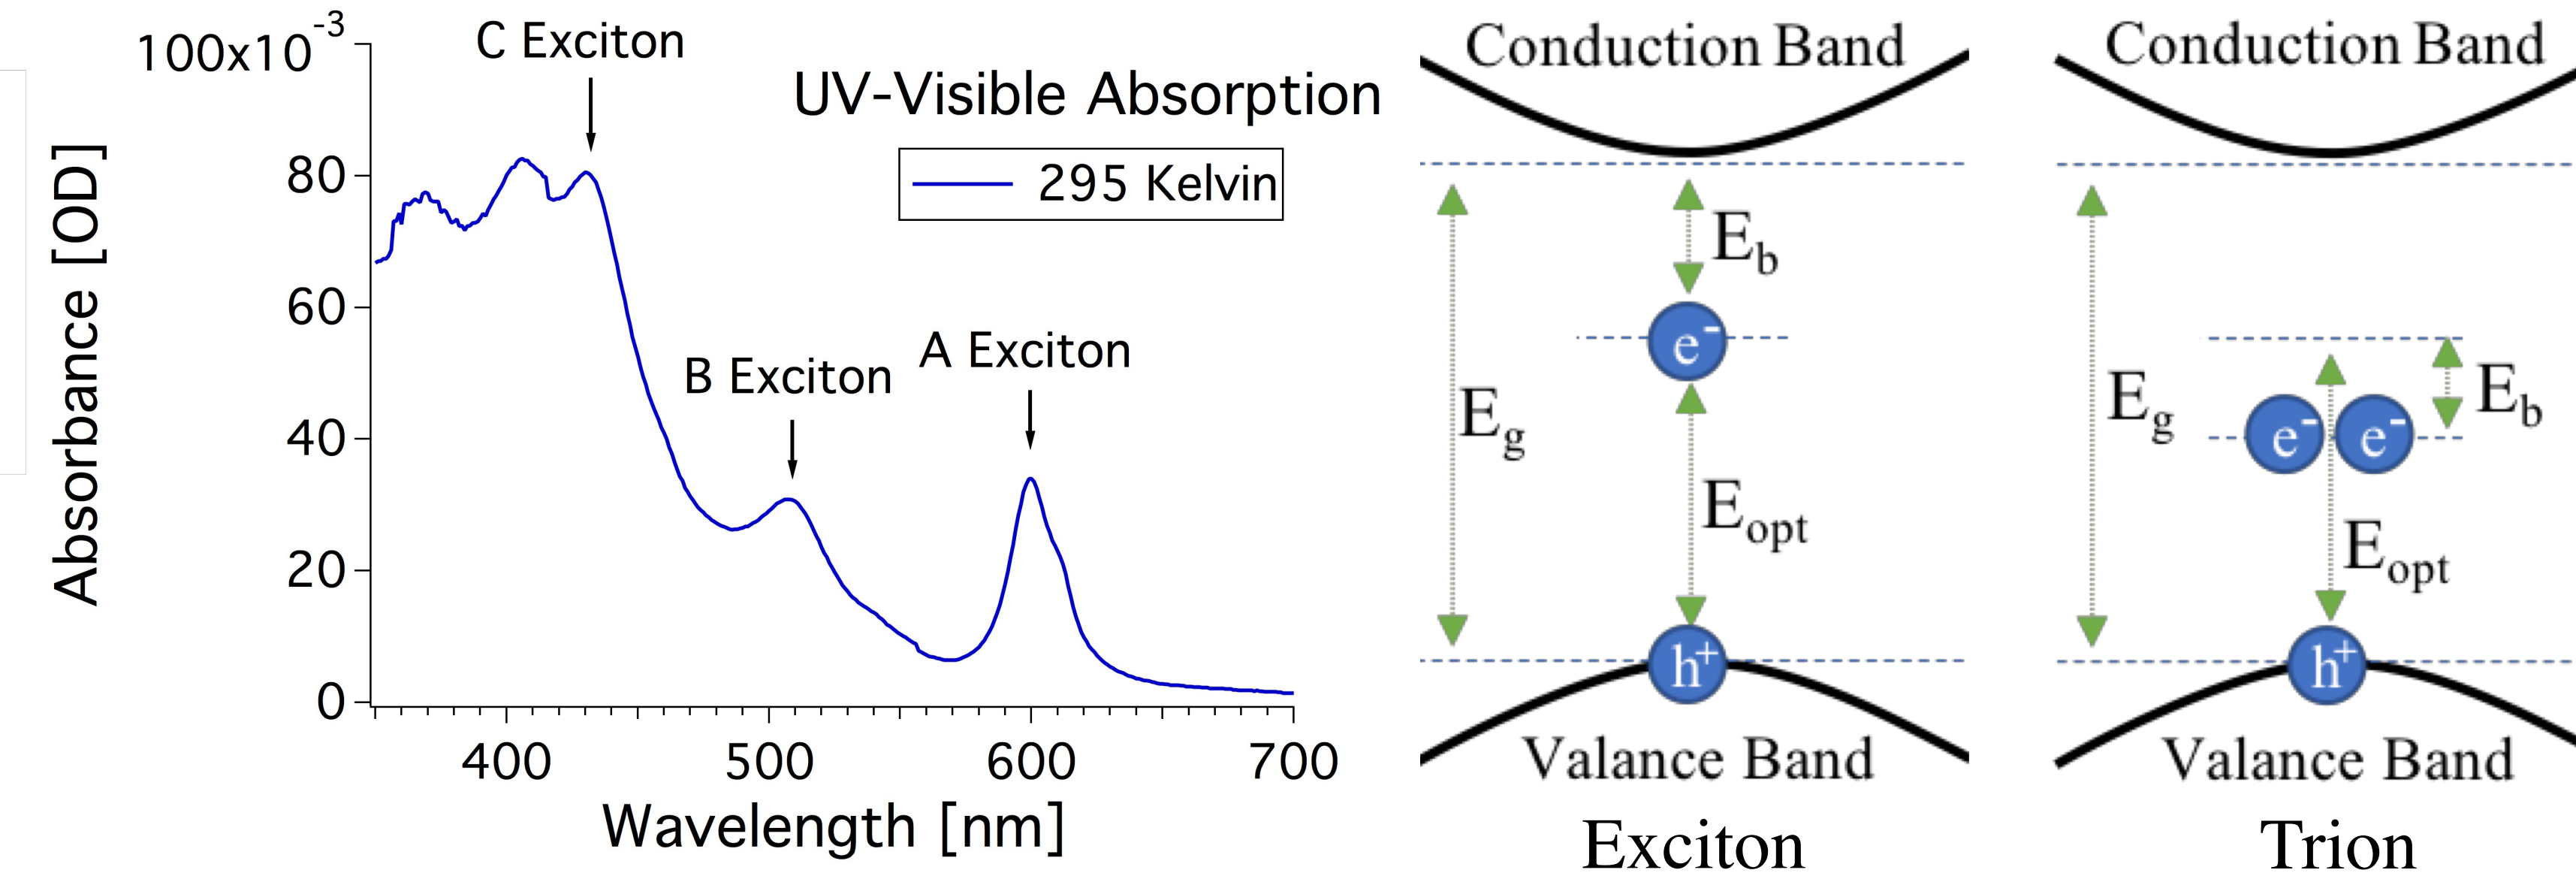


## Time-Resolved Terahertz Spectroscopy (TRTS)

- TRTS probes the photo-generated excited state of a material with sub-picosecond resolution
- Yields complex frequency-dependent conductivity

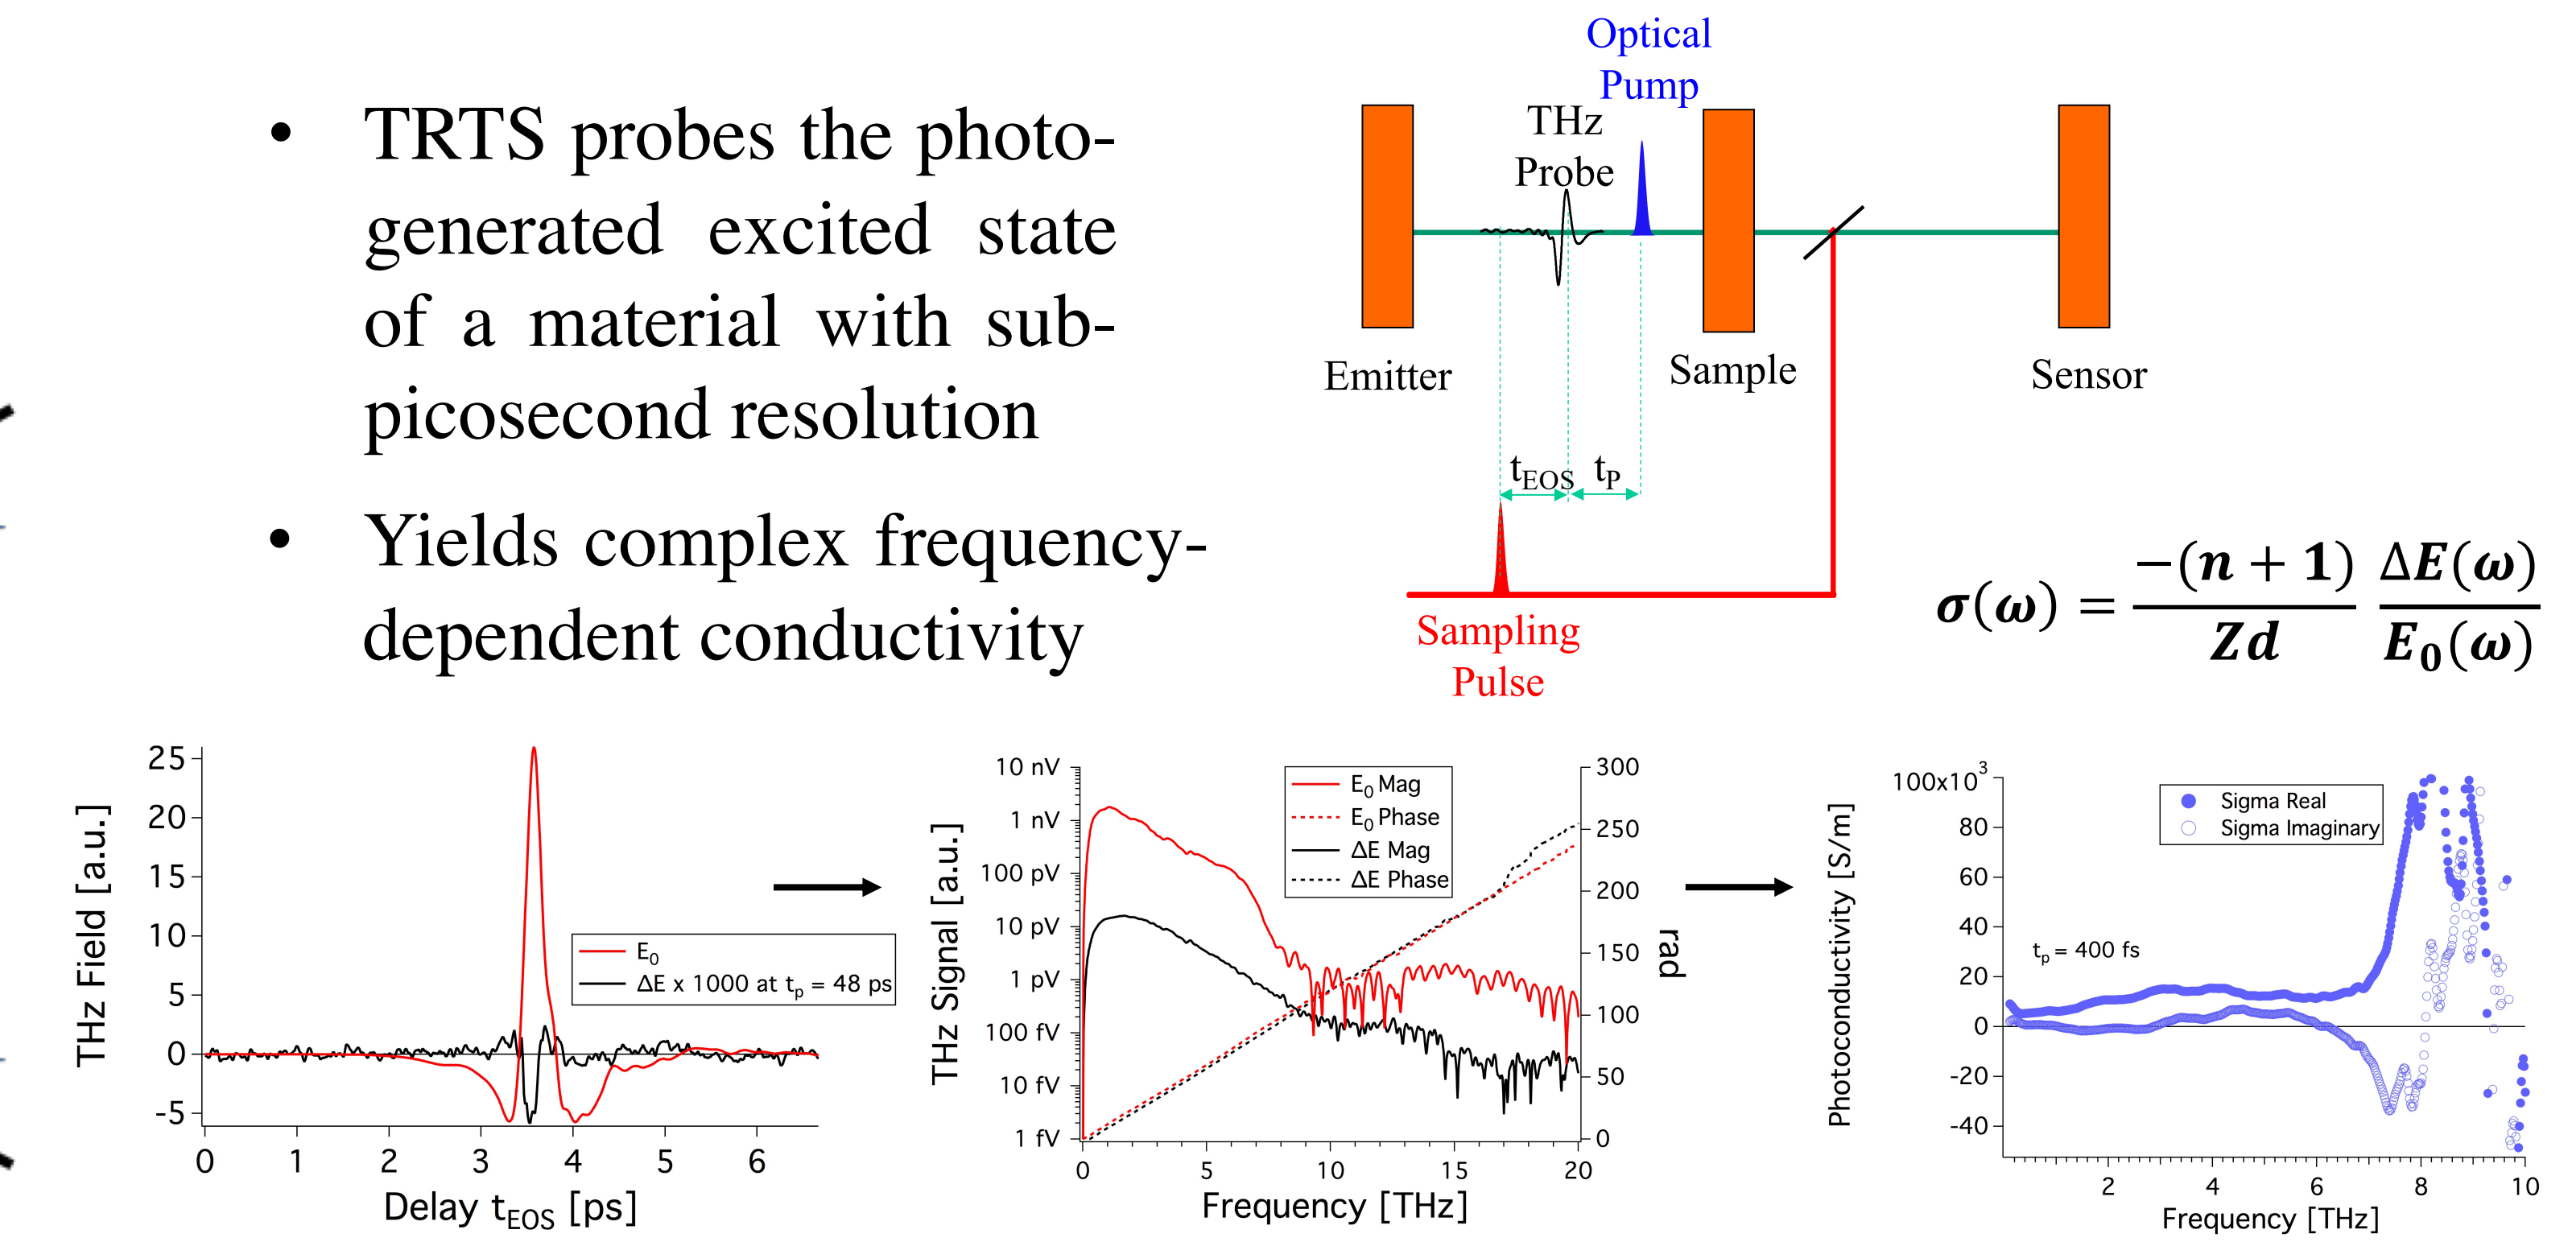

## Time Evolution of Photoconductivity

- Conductivity was probed at pump delays  $t_p = 0.6, 1, 3,$  and  $5$  ps at 20 Kelvin with  $\sim 6 \times 10^{14}$  photons/cm<sup>2</sup> of 584 nm

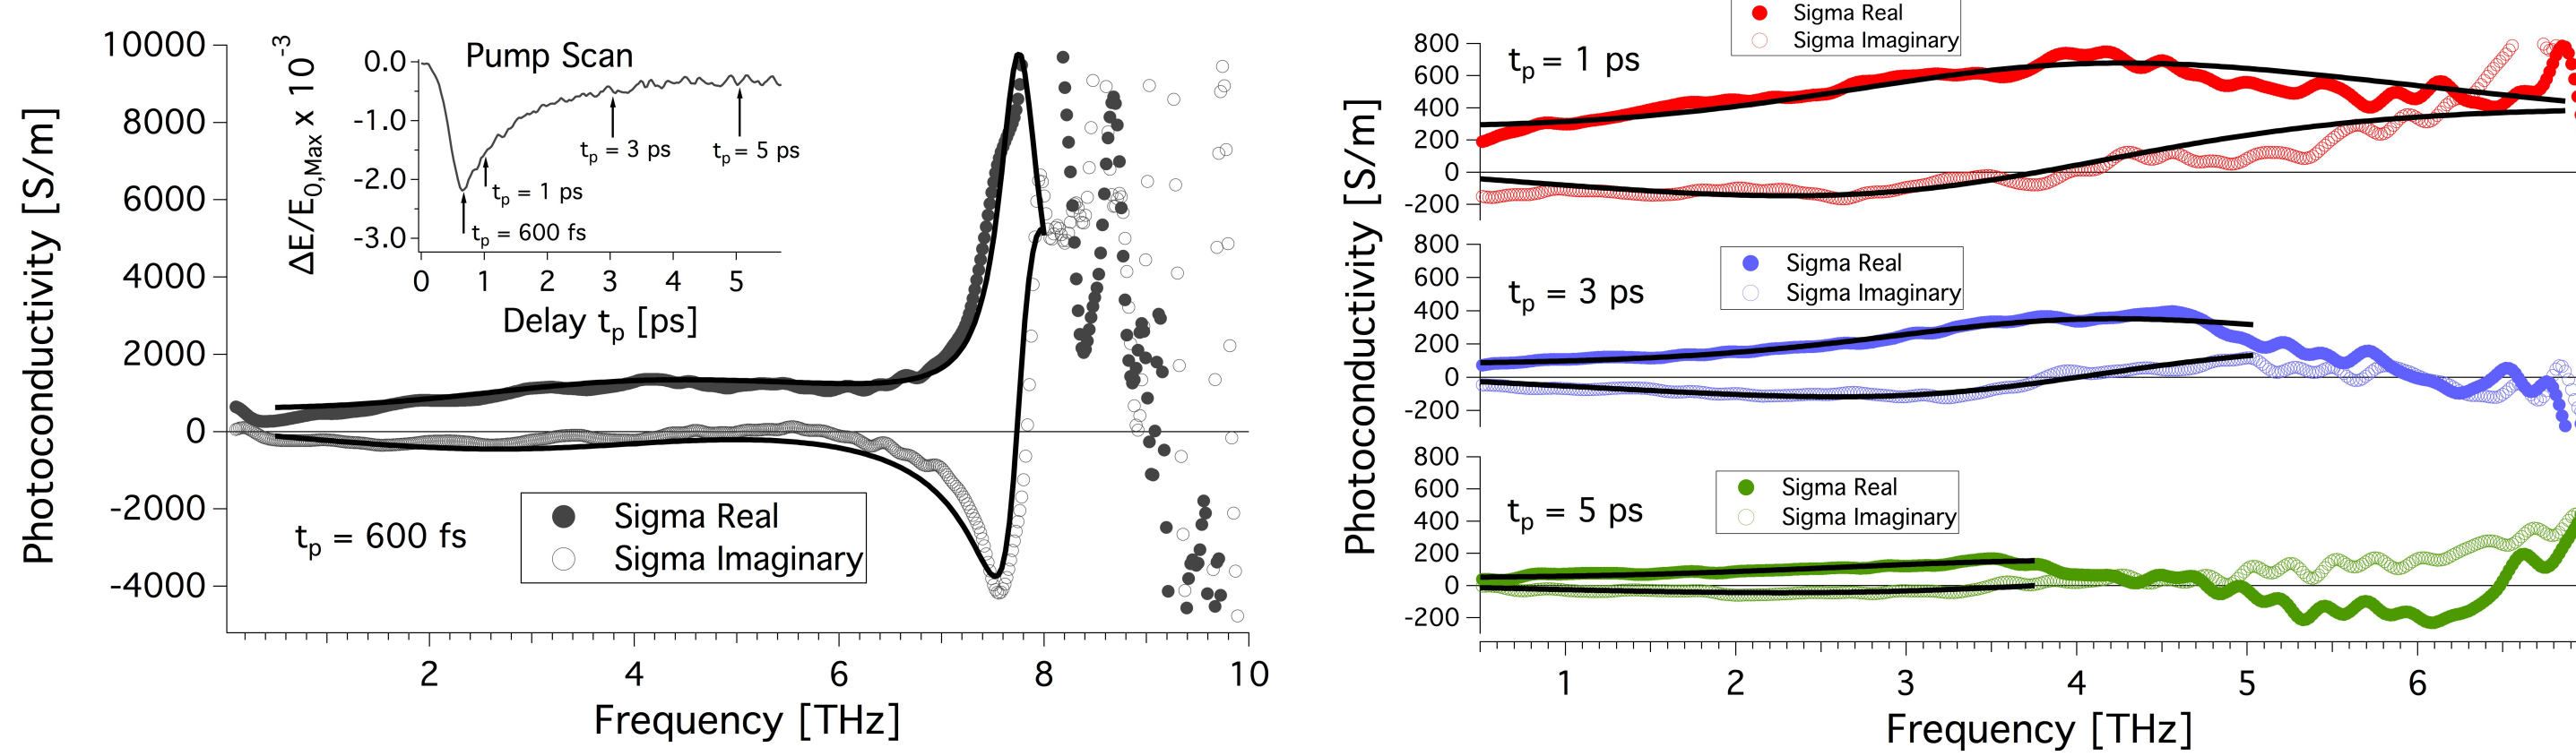

- Trions have been predicted<sup>2,3</sup> and observed<sup>1,4,5,6,7</sup> to have binding energies of about 25-40 meV ( $\sim 6.0$ -9.7 THz) in WS<sub>2</sub>
- The resonant feature in the conductivity at 7.75 THz (32meV) indicates the formation of trions in our sample
- We model the THz photoconductivity as a sum of three oscillators

$$\sigma(\omega) = \sum_{m=1}^3 \frac{i C_m \omega}{\omega^2 - \omega_{0m}^2 + i \omega \gamma_m}$$

$C_m \equiv$  Spectral weight  
 $\gamma_m \equiv$  Linewidth (THz)  
 $\omega_{0m} \equiv$  Resonant frequency (THz)


$m = 1 \rightarrow$  Drude Response     $m = 2 \rightarrow$  Plasma Response     $m = 3 \rightarrow$  Trion Response

Pump Delay	$C_1$	$\gamma_1$	$\omega_{01}$	$C_2$	$\gamma_2$	$\omega_{02}$	$C_3$	$\gamma_3$	$\omega_{03}$
$t_p = 600$ fs	1.5e16	25.0	0	4.4e16	41	4.7	2.6e16	2.93	7.75
$t_p = 1$ ps	7.8e15	27.0	0	1.9e16	35	4.5	0	0	0
$t_p = 3$ ps	3.9e15	44.9	0	7.5e15	26	4.3	0	0	0
$t_p = 5$ ps	2.1e15	41.1	0	3.3e15	27	4.1	0	0	0

- There is no trion component for pump delays of  $t_p = 1, 3,$  and  $5$  ps
- As  $t_p$  increases,  $\omega_{02}$  shifts to lower frequencies

## Fluence-Dependent Photoconductivity


- Conductivity was probed on resonance (A exciton) at 20 Kelvin (557 nm pump) at various fluences 400 fs after excitation

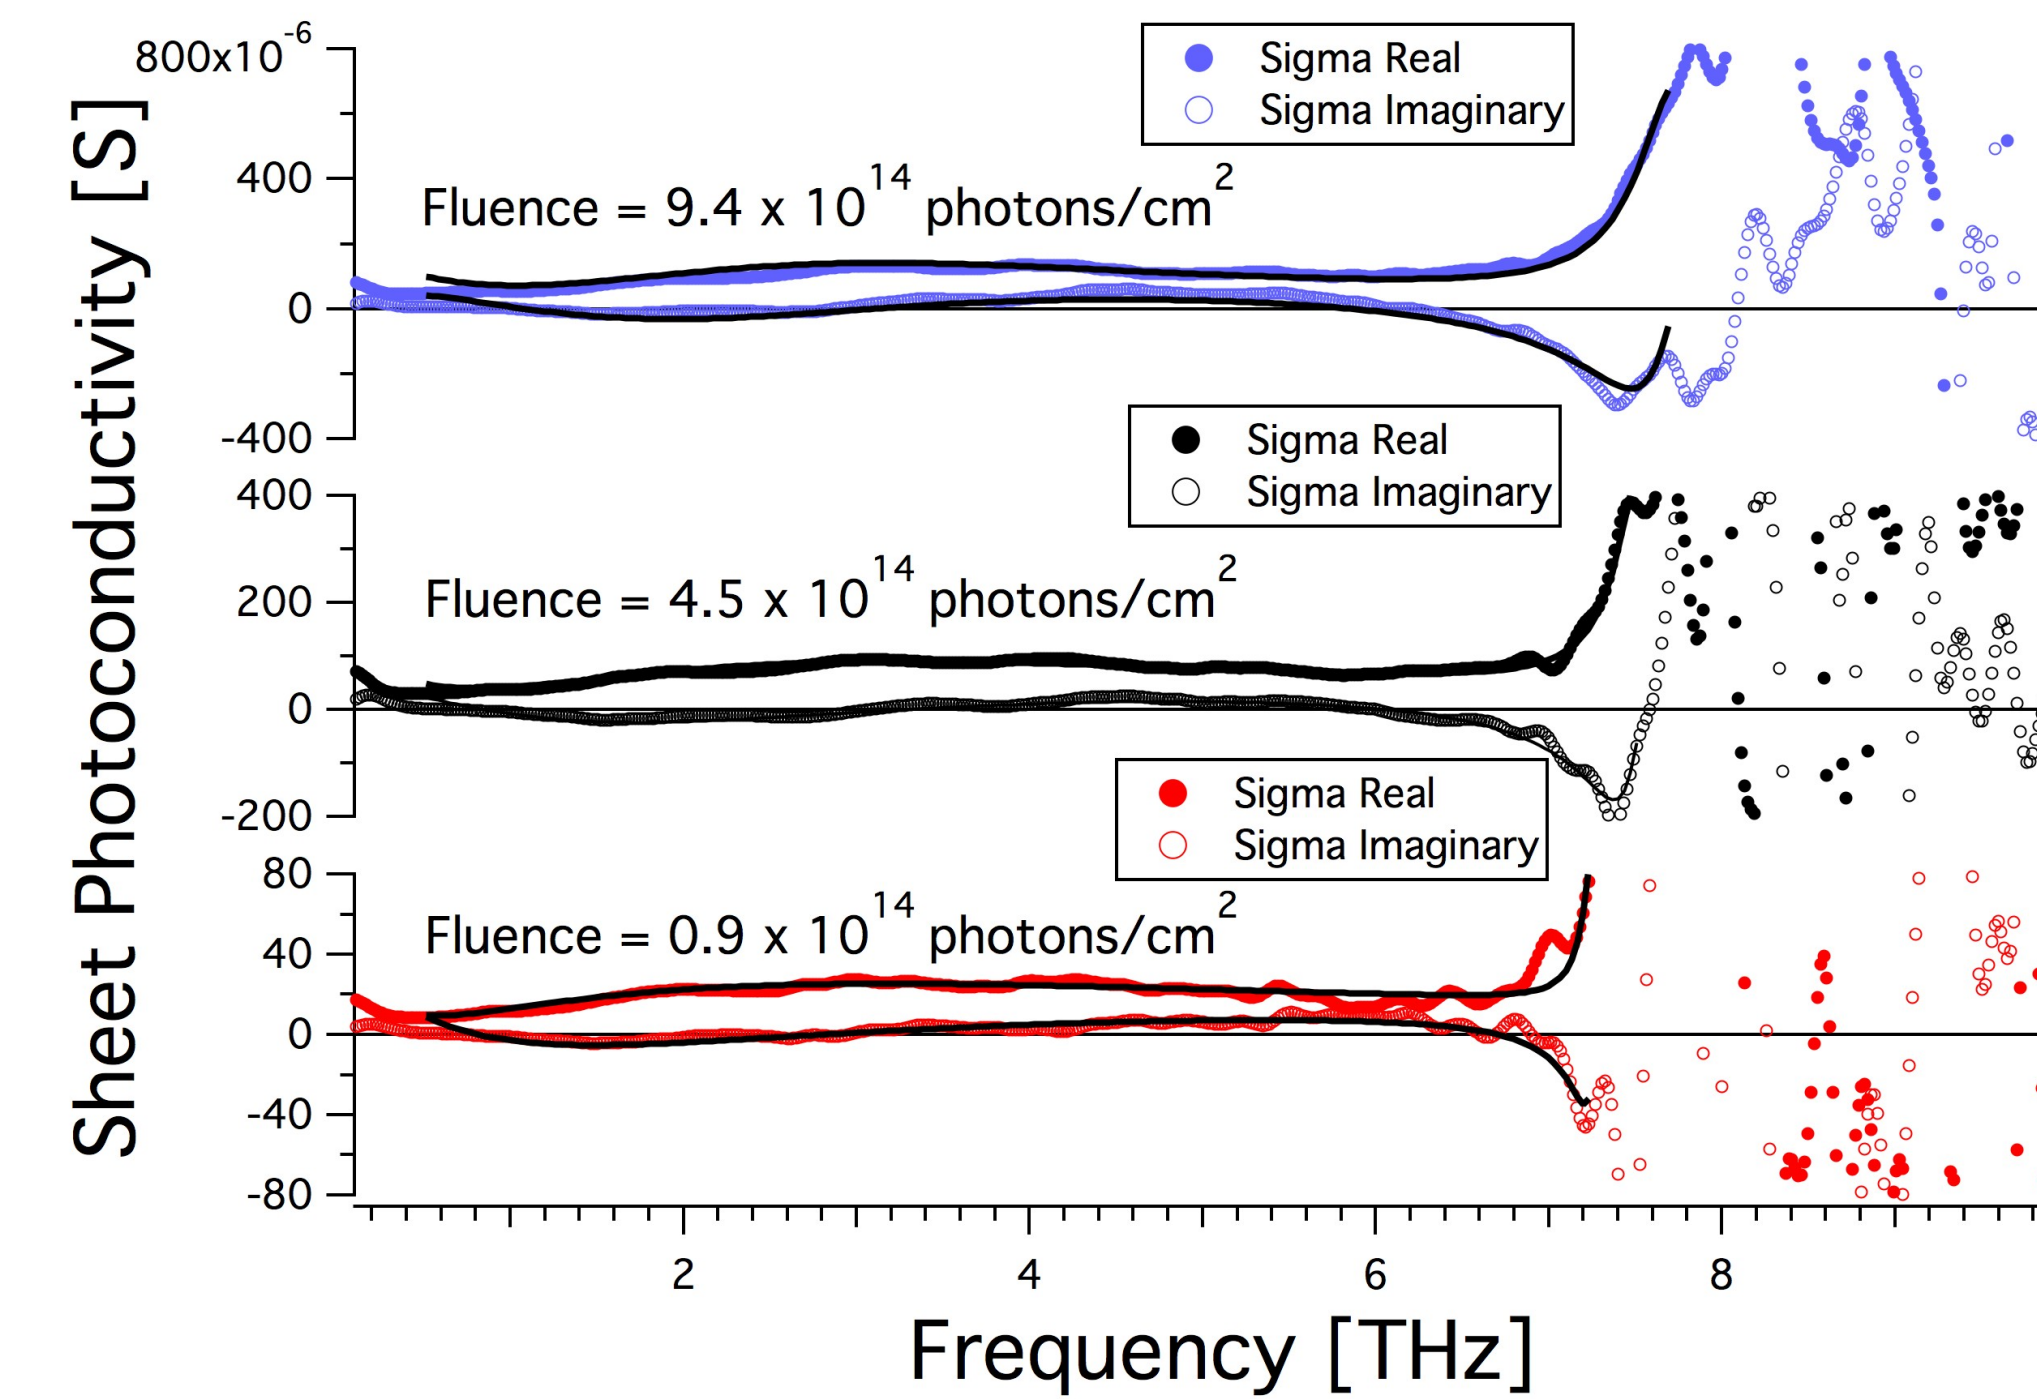

Fluence	$C_1$	$\gamma_1$	$\omega_{01}$	$C_2$	$\gamma_2$	$\omega_{02}$	$C_3$	$\gamma_3$	$\omega_{03}$
9.4e14	6.0e8	3.8	0	4.3e9	32	3.2	2.3e9	3.55	7.75
4.5e14	2.6e8	2.6	0	3.7e9	42	3.3	1.0e9	2.31	7.56
0.9e14	6.5e7	1.0	0	1.3e9	53	3.2	9.9e7	1.02	7.29

- Trion component observed at all fluences


- As  $t_p$  increases:
  - No trend in  $\omega_{02}$
  - $\omega_{03}$  shifts to lower frequencies

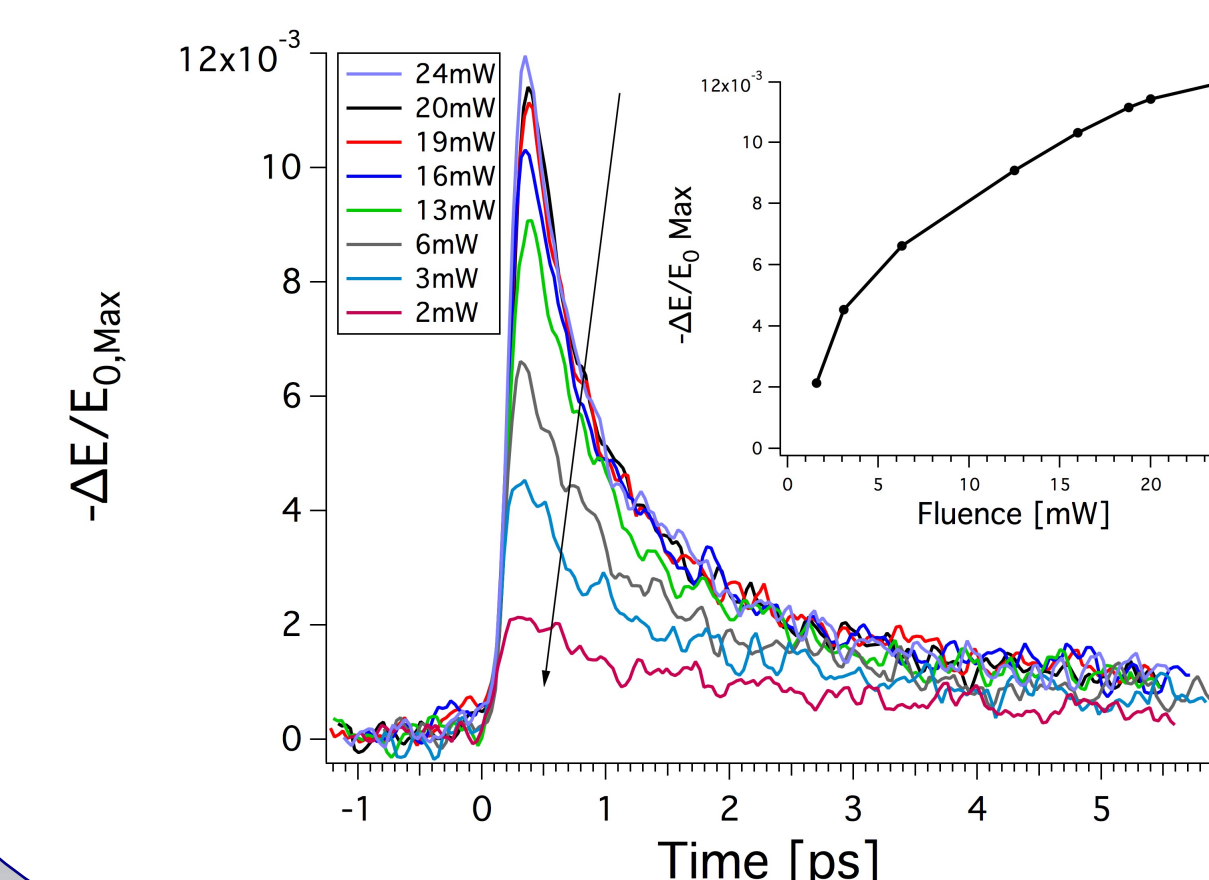

- As fluence increases, the change in the THz field saturates
- Free charge carriers are no longer being generated

## Above and Below Resonant Excitation

- Conductivity was probed above the bandgap (400 nm pump) and on resonance (557 nm) at 20 Kelvin

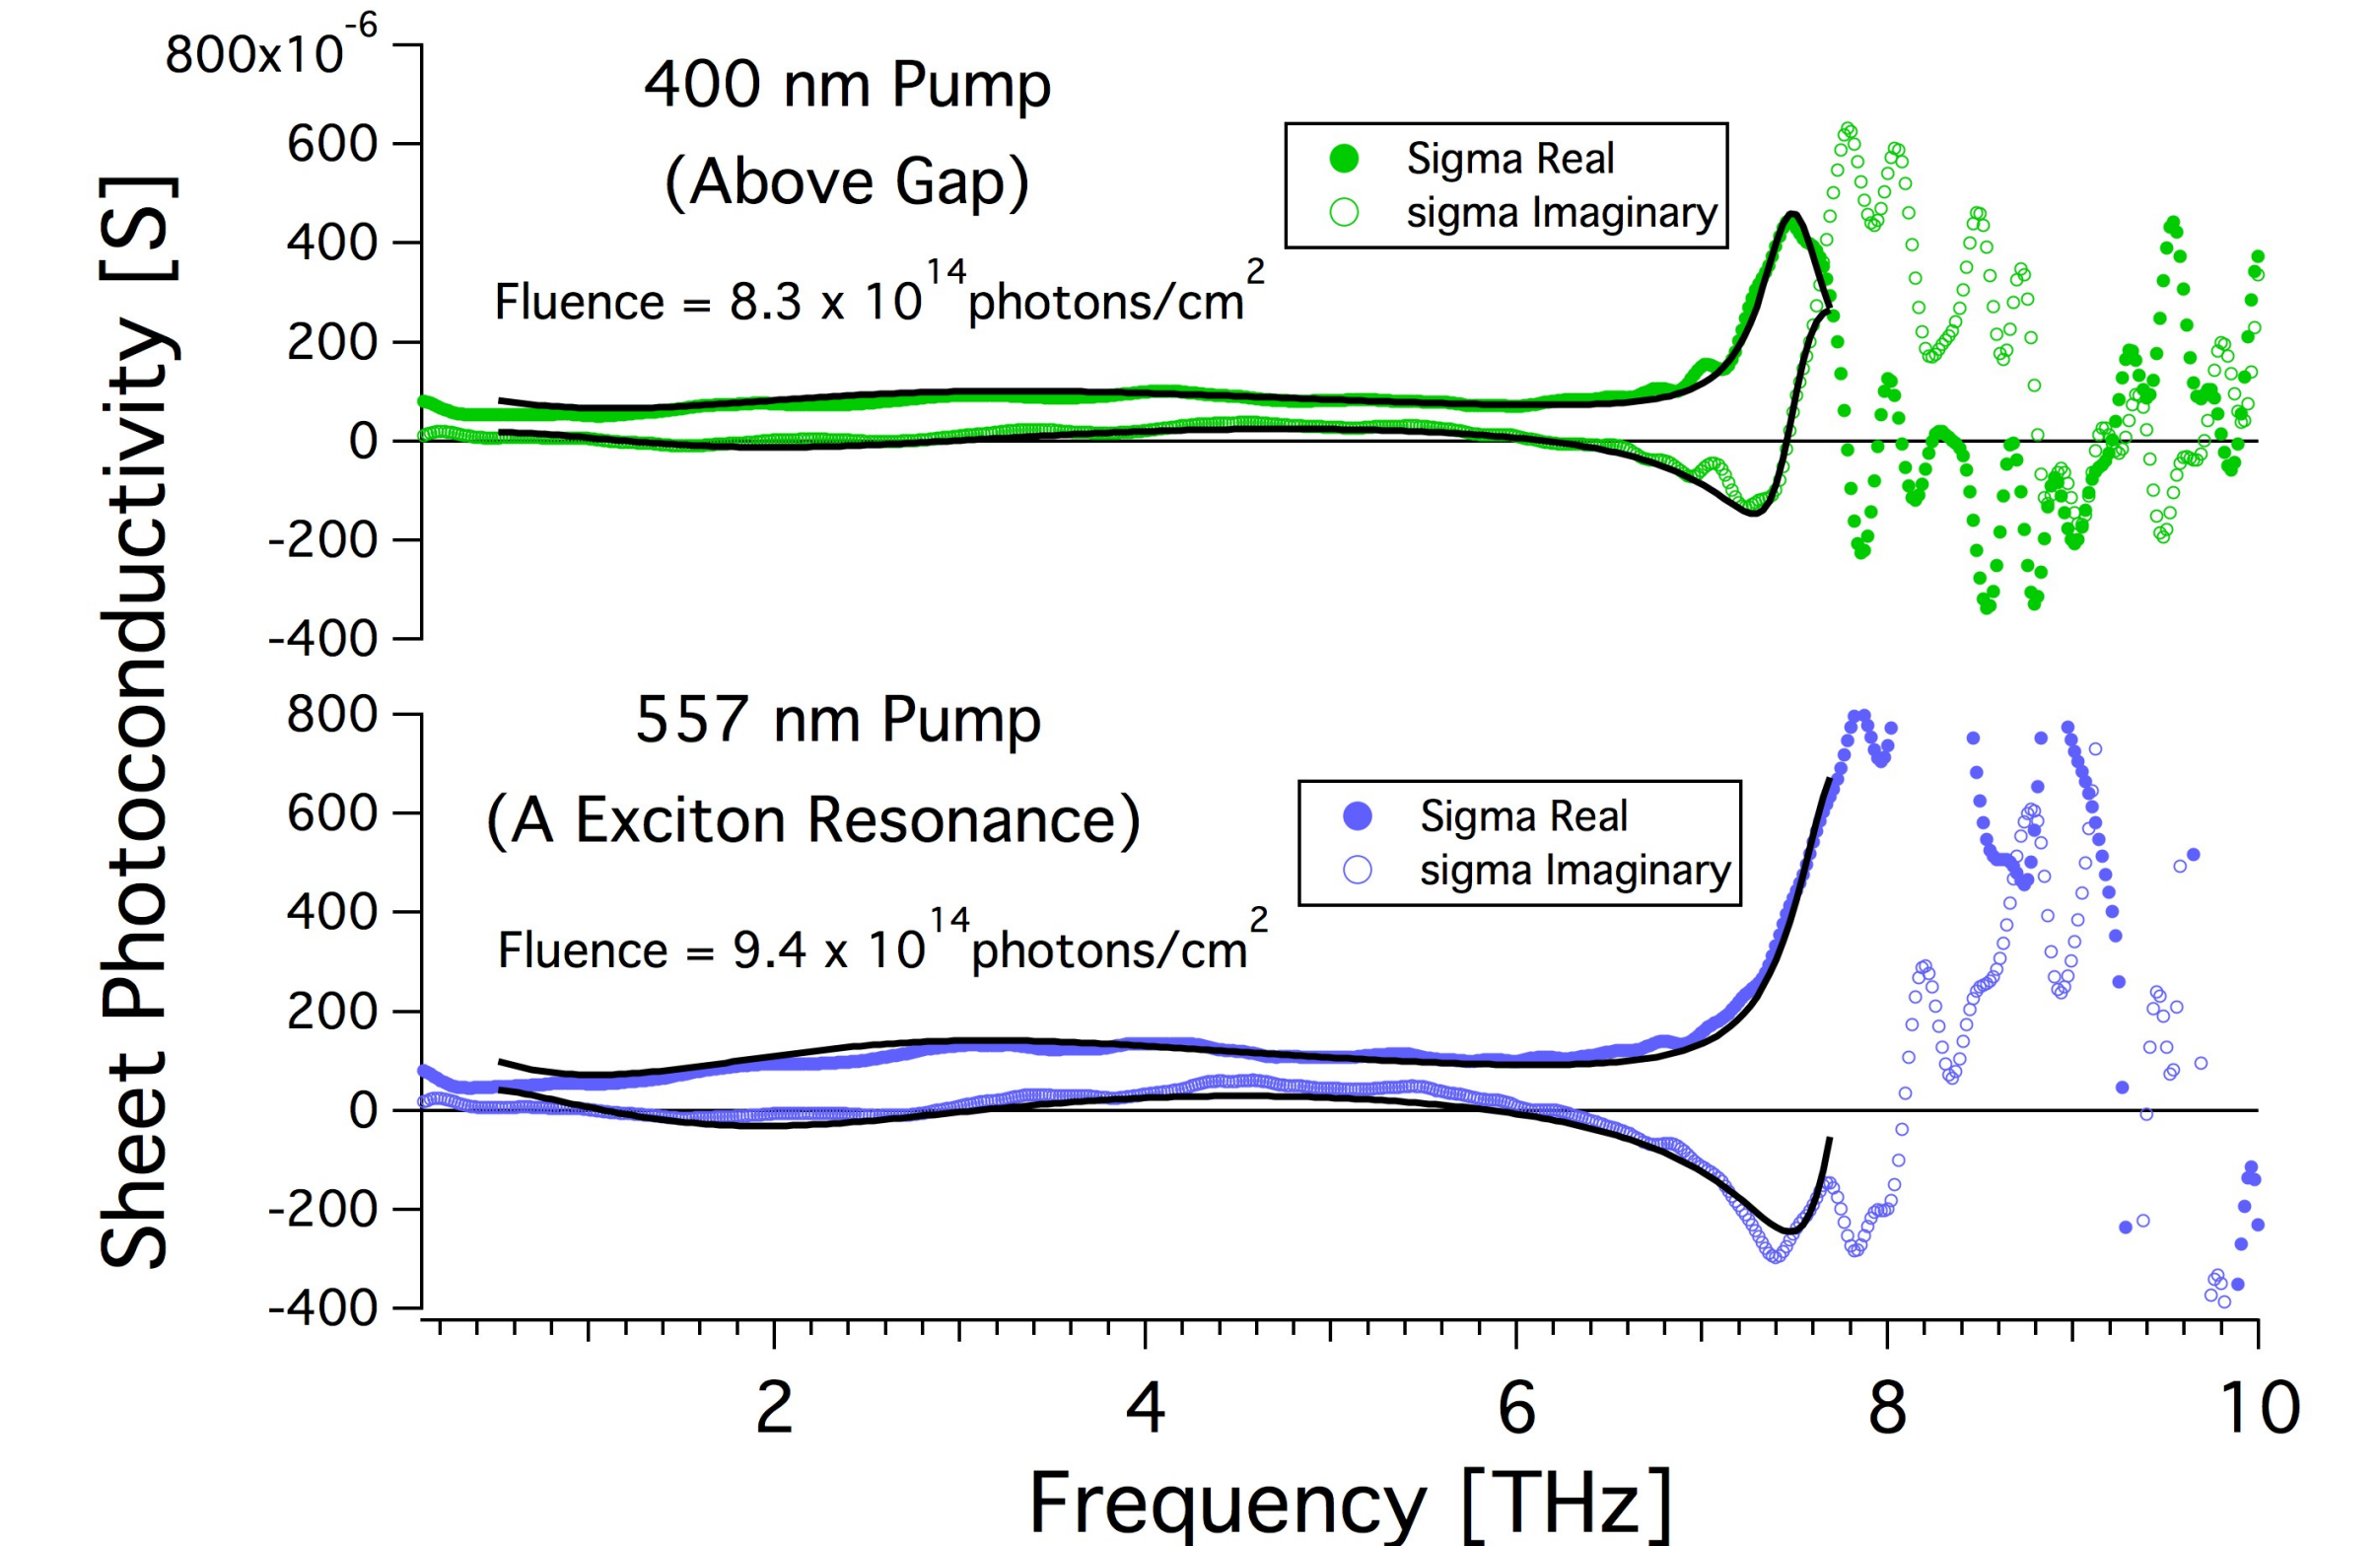

## Conclusions

- We attribute the Drude response to the promotion of trapped defect electrons to the conduction band
- We assign the source of the  $\omega_{02}$  resonance to a plasmonic<sup>8</sup> response associated with particles with sizes similar to the THz wavelengths
- We assign the source of the  $\omega_{03}$  resonance to the dissociation of trions into free electrons and excitons

## References

- Zhu et al., *Scientific Reports* **5** 9218 (2015)
- Berkelbach et al., *Phys Rev B* **88** 045318 (2013)
- Kezerashvili et al., *Few Body Syst* **58** 18 (2017)
- Chernikov et al., *Phys Rev Lett* **113** 076802 (2014)
- Mitioglu et al., *Phys Rev B* **88** 245403 (2013)
- Peimyoo et al., *ACS Nano* **8** 11 (2014)
- Plechinger et al., *Phys Status Solidi* **9** 8 (2015)
- H.-K. Nienhuys and V. Sundstrom, *Appl. Phys. Lett.* **87** 012101 (2005)